arXiv:cond-mat/9912333v1 [cond-mat.supr-con] 17 Dec 1999

In–Plane and Out–of–Plane Optical Properties of $NdBa_2Cu_3O_x$ Single Crystals close to x = 7.0

R. Hauff[*], M. Göppert[⋆], B. Obst[*], Th. Wolf[*], P. Schweiss[‡], and H. Wühl[*,†]

Forschungszentrum Karlsruhe, [*]ITP and [‡]INFP, 76021 Karlsruhe, Germany
Universität Karlsruhe, [†]IEKP and [⋆]AP, 76128 Karlruhe, Germany

We present results of reflectivity measurements with $\mathbf{E}\|\mathbf{c}$ *and* $\mathbf{E} \perp \mathbf{c}$ *on* $NdBa_2Cu_3O_x$ *(Nd123) single crystals close to full oxygen doping. Along the c–axis the optical conductivity* σ_1^c *shows a well developed absorption band around 450* cm^{-1} *at all temperatures. The in–plane optical properties are dominated by crystal–field excitations at low energies, a prominent step at 400* cm^{-1} *and a weaker feature between 500 - 550* cm^{-1}*. A comparison of* σ_1^c *and the in–plane scattering rate* $\Gamma_{ab}(\omega)$ *with neutron scattering derived spin susceptibility spectra suggests that the in–plane and out–of–plane anomalies are caused by the same mechanism, probably electron–spin scattering.*

PACS numbers: 74.25.-q, 74.72.-h, 78.30.-j

Besides its low–frequency suppression, the normal state c–axis conductivity $\sigma_1^c(\omega)$ of underdoped Y123 shows two other prominent features, namely the development of an absorption band around 450 cm^{-1} and an anomalous softening of the oxygen bending phonon at 320 cm^{-1} which is accompanied by a loss of spectral weight[1,2]. Although we were able to show that the absorption band is not related to the suppression of the conductivity[3], its nature is still not clear. So far, a variety of explanations have been suggested, e.g. regarding it as a new phonon[1], a bilayer plasmon[4] or as being caused by spin–phonon coupling[3]. On the other hand, in Y123 the in–plane conductivity σ_1^{ab} also shows an anomaly in that frequency range[5], and there may be a connection between these in–plane and out–of–plane anomalies.

We performed reflectivity measurements both parallel and perpendicular to the c–axis of Nd123 single crystals. The Nd123 system was chosen because good quality crystals are available and it is possible to study the

effects caused by the substitution of the bigger Nd ion for the Y ion.

The $NdBa_2Cu_3O_x$ samples were grown as described elsewhere[6] and showed the usual twinning. The oxygen content x was adjusted by annealing in flowing oxygen at different pressures and temperatures. This yielded x = 6.99 and x = 6.96, determined by isobars after Lindemer et al.[7] and cross–checked by neutron scattering. The specific–heat T_c was 95.5 K (93.5 K) for the x = 6.99 (6.96) crystal. EDX analysis found that 8 % of the Nd sites were occupied by Y, probably caused by the crucible. As a result our samples showed a slightly higher T_c than Y–free Nd123 crystals with the same oxygen content[8]. However, apart from this T_c effect, we regard the Y contamination as not crucial for the present study. Due to its small dimension in c–direction the $NdBa_2Cu_3O_{6.99}$ crystal was measured only in the ab–plane without using a polarizer. The spectra of the $NdBa_2Cu_3O_{6.96}$ sample were taken on an (a,b)c–plane with both $\mathbf{E}\|\mathbf{c}$ and $\mathbf{E} \perp \mathbf{c}$. The measurements were performed in a Fourier transform spectrometer in the frequency range 40 - 7000 cm^{-1} and at 10 - 300 K. The spectral region of 3000 - 40000 cm^{-1} was measured in a prism spectrometer at room temperature. As reference a gold and an aluminum mirror have been used.

Fig.1a shows the Kramers–Kronig calculated c–axis optical conductivity of $NdBa_2Cu_3O_{6.96}$ at various temperatures. The main features of the spectra are a strong absorption band around 450 cm^{-1} far above T_c and the lack of normal–state anomalies of the oxygen bending phonon at 320 cm^{-1}. This last observation clearly speaks against an interpretation of the absorption band as a new phonon growing on the expense of other modes as suggested by Homes et al.[1]. Furthermore, it shows that in contrast to what we claimed earlier[3], the absorption band is probably not related to the phonon system at all. On the other hand, the fact that both the absorption band and the phonon anomalies simultaneously disappear in Zn–substituted crystals[3] indicates that, although the two phenomena are not causally related to each other, they still might originate from the same mechanism, e.g. by coupling to the same kind of excitations. Finally, we want to mention that the above results are different to what can be found in $YBa_2Cu_3O_x$ compounds: firstly, in the latter the absorption band develops for temperatures $\lesssim$ 150 K, whereas in Nd123 it can be observed up to room temperature (not shown). Secondly, in Y123 this band is well known in underdoped samples with x $\lesssim$ 6.7, in samples with x = 6.96, however, it has never been observed. This indicates that despite the high oxygen content the hole doping level of the $NdBa_2Cu_3O_{6.96}$ sample is relatively low which also shows in the in–plane reflectivity (Fig.1b and c). In Fig.1b we compare the reflectivity of both Nd123 samples at 100 K with the results of Orenstein et al.[5] on twinned Y123. In the mid infrared the fully oxygenated Nd123 sample behaves like a Y123 crystal with T_c =

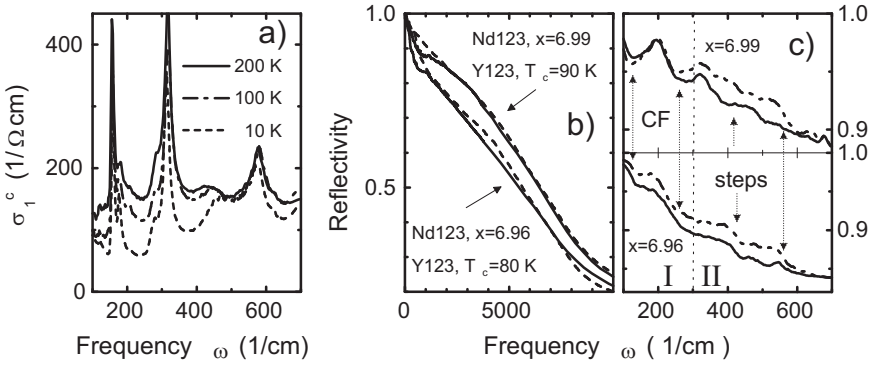

Fig. 1. a) c–axis conductivity σ_1^c of $NdBa_2Cu_3O_{6.96}$. b) in–plane reflectivity of $NdBa_2Cu_3O_x$ with x = 6.99 and x = 6.96 (solid lines) at T = 100 K compared to the results for Y123 with T_c´s of 90 K and 80 K (dashed lines, Ref.5). c) in–plane reflectivity of Nd123 at 100 K (solid lines) and 10 K (dashed lines). Region I is dominated by crystal–field (CF) excitations, in region II there are steps around 400 cm^{-1} and 500 - 550 cm^{-1}.

90 K, whereas the $NdBa_2Cu_3O_{6.96}$ crystal resembles Y123 with a T_c of only 80 K, albeit with a less developed shoulder around 4000 cm^{-1}. As this band is usually ascribed to excitations in the CuO–chains[5], this may indicate that in oxygen reduced Nd123 the chains are more fragmented than in Y123 resulting in a lower hole concentration which is in accord to Widder et al.[9]. In the far infrared (FIR) the reflectivity of both Nd123 crystals shows several characteristic features (Fig.1c). The FIR can be divided into two regions: region I is dominated by features at 160 and 300 cm^{-1}, in region II there are steps in the reflectivity around 400 and 550 cm^{-1} which are visible at all temperatures becoming more pronounced at lower temperatures. We ascribe the region–I features to Nd^{3+} crystal–field excitations as they appear almost exactly at the same positions as calculated by Martin et al.[10]. Concerning region II, similar structures have been observed in a variety of compounds and have been explained in terms of a coupling of the mid–infrared continuum to longitudinal optical (LO) c–axis phonons[11]. However, this interpretation can not apply to our spectra, because the structures are also visible in the reflectivity measured on an (a,b)c–surface, a geometry where a coupling to LO c–axis modes is forbidden.

As an interpretation for this region–II features we rather suggest scattering of the electrons by spin excitations as described below. Using an one–component analysis we calculated for the $NdBa_2Cu_3O_{6.96}$ sample the

low–temperature frequency–dependent in–plane scattering rate Γ_{ab} shown in Fig.2a. Additionally, we plotted Γ_{ab} of twinned Y123 (T_c = 92 K) after Liu et al.[12] which shows the in these samples generally observed non–linear suppression below 1000 cm^{-1}. In fully doped untwinned Y123 this suppression is only seen in the b–axis component of Γ[13], in underdoped material there is also a suppression in the a–axis component[14]. Comparing the Nd123 and Y123 spectra of Fig.2a suggests that this behaviour is also present in Nd123, but masked between 100 - 1000 cm^{-1} by strong additional contributions. In order to extract these contributions, we used Γ_{ab}(Y123) as a background and subtracted it from Γ_{ab}(Nd123) yielding the difference spectrum of Fig.2c. Hereby, we assumed that Γ_{ab}(Y123) describes the generic decrease, free of spin scattering contributions which seems to be reasonable considering the weak spin spectrum of fully doped Y123 (Fig. 2b). In region I the enhancement of Γ_{ab} is probably caused by the crystal–field excitations mentioned above, which have nothing to do with the following scenario and are therefore not further considered, while we ascribe the enhanced scattering rate in region II to electron–spin interaction. We assume a model spin susceptibility χ_{model} for $NdBa_2Cu_3O_{6.96}$ (Fig.2b and c) which possesses the

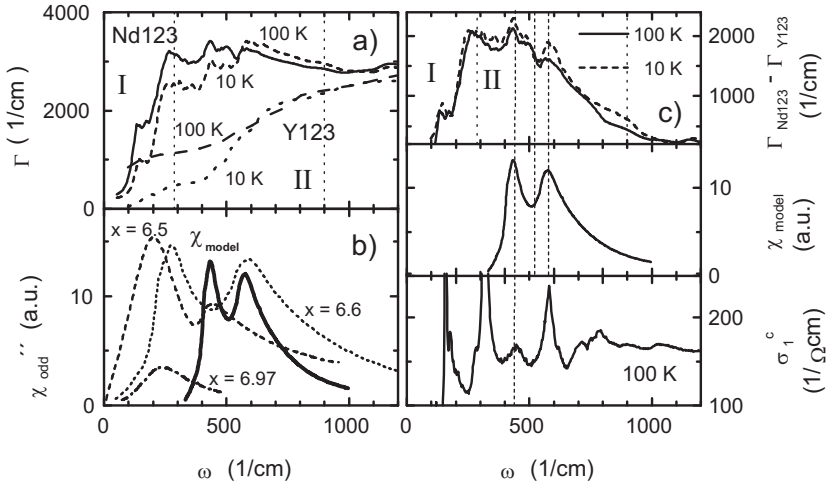

Fig. 2. a) In–plane scattering rate Γ_{ab} of $NdBa_2Cu_3O_{6.96}$ and fully doped Y123 (Ref.12). b) Low temperature spin susceptibility χ" of $YBa_2Cu_3O_x$ at various x (Ref.15). The right peak develops only at low T. χ_{model} (thick line) is a model susceptibility we assume for $NdBa_2Cu_3O_{6.96}$. c) Difference of Γ_{ab} for Nd123 and Y123 of a) compared to χ_{model} and $\sigma_1^c(100K)$.

same double–peak structure as the neutron–scattering derived spectra χ" of underdoped Y123[15], but has a gap at low energies which accounts for the fact, that with increasing oxygen content the low–energy spin excitations disappear[15]. The size of the gap may be justified if we consider that the big Nd ion causes an expansion of the unit cell compared to Y123 which may alter the spin exchange interaction in the Nd system resulting in a larger gap. With this χ_{model} we are able to reproduce the two peaks at 400 and 550 cm^{-1} in the difference spectrum of Fig.2c as well as the peak in the conductivity σ_1^c. In this scenario the left peak in χ_{model}, present already at 300 K, causes the absorption band, whereas the 320 cm^{-1} phonon lying in the gap region is not affected. In Y123, on the other hand, the left peak of the measured χ" roughly coincides with the 320 cm^{-1} phonon and the right peak with the absorption band position. This then may lead to the observed phonon anomalies and the growth of the absorption band when the left peak shifts to lower energies and the right peak develops with decreasing temperature as seen by Bourges et al.[15].

In summary, by optical measurements we found anomalies in the in–plane and out–of–plane properties of highly oxygenated Nd123. The anomalies are similar to the ones observed in underdoped Y123 and are probably caused by electron–spin interaction.

REFERENCES

1. C. C. Homes et al., *Phys. Rev. Lett.* **71**, 1645 (1993) and *Can. J. Phys.* **73**, 663 (1995).
2. J. Schützmann et al., *Phys. Rev. B* **52**, 13665 (1995).
3. R. Hauff et al., *Phys. Rev. Lett.* **77**, 4620 (1996).
4. M. Grüninger et al., *preprint cond-mat/9903352.*
5. D. B. Tanner and T. Timusk in *Optical Properties of High Temperature Superconductors III*, ed. D. M. Ginsberg, (World Scientific, Singapore, 1992), p. 363 and references therein.
6. Th. Wolf et al., *Phys. Rev. B* **56**, 6308 (1997).
7. T. B. Lindemer et al., *Physica C* **255**, 65 (1995).
8. A. Erb et al., *Applied Superconductivity, Proc. of EUCAS* 1997, 1109 (1997).
9. K. Widder et al., *Physica C* **251**, 274 (1995).
10. A. A. Martin et al., *Phys. Rev. B* **59**, 6528 (1999).
11. M. Reedyk and T. Timusk, *Phys. Rev. Lett.* **69**, 2705 (1992).
12. H. L. Liu et al., *J. Phys.: Condens. Matter* **11**, 239 (1999).
13. N. L. Wang et al., *Phys. Rev. B* **57**, R11081 (1998).
14. A. V. Puchkov et al., *J. Phys.: Condens. Matter* **8**, 100049 (1996).
15. L.P. Regnault et al. in *Neutron Scattering in Layered Copper–Oxide Superconductors*, ed. A. Furrer, (Kluwer Academic Publishers, 1998), p. 85 and references therein; S. M. Hayden et al., *cond-mat/9710181.*